



STRUCTURAL, OPTICAL AND MECHANICAL PROPERTIES OF ORGANIC SINGLE CRYSTAL: 4-N, N-DIETHYLAMINO-4- N-METHYL-STILBAZOLIUM IODIDE (DESI)

¹Priya Antony, ¹S. John Sundaram, ²Dominique, ¹A. Antony Raj, ¹P. Sagayaraj

¹Department of Physics, Loyola College (Autonomous), Chennai -34

²Department of Physics, St. Joseph's College, Tiruchirappalli – 02

ABSTRACT- Organic stilbazolium family single crystal 4-N, N-diethylamino-4-N-methyl-stilbazolium Iodide (DESI) has been successfully grown from aqueous methanol solution by adopting slow solvent evaporation technique. Single crystal X-ray diffraction analysis was carried out and it shows that DESI crystal belongs to triclinic structure with P-1 space group. Its absorption spectrum was found by UV-Vis spectrum. Hardness study was also carried out for applying different loads.

Keywords- [Organic compound; X-ray diffraction; Hardness study]

1. INTRODUCTION

The design and synthesis of organic materials for high second order nonlinear optical effect has become an important research area due to their potential and wide applications in the fields of optical signal processing, integrated photonics, optical switching, optical data storage, bioimaging, electro-optic modulation, spectroscopy and THz wave generation and detection. Further, the presence of styryl pyridinium compounds is being mainly used as antibacterial drugs, herbicides, environmental disinfection, disinfection in hospital environments and food industry due to their low toxicity to humans and animals. Hence, the efforts have been made to engineer the novel π -conjugated organic molecules because of their second and third-order nonlinear optical activities. Ionic organic crystals with high chromophore density are of special interest for large NLO

effect[1-3]. The stable packing of chromophores in these crystals results in high thermal, mechanical and photochemical stability. The design of NLO chromophore crystals has an electron withdrawing group that bear an electron donating group interacting through the π -conjugated system with parallel alignment in the crystal structure. The formation of the carbon-carbon bridge (C=C) with π -conjugation chromophores of an organic molecule can be obtained by Knoevenagel condensation reaction. This method is most favorable and easy method for to form a carbon-carbon double bond. By engineering the organic chromophore many crystals has been grown, among that one such material is 4-N, N-diethylamino-4-N-methyl-stilbazolium iodide(DESI). This single crystal has been grown by adopting slow evaporation solution growth technique. In this

article, we report the Structural, optical and mechanical properties of the title compound.

Synthesis and Crystal growth

DESI was synthesized by employing, the condensation of 1,4 dimethylpyridinium iodide and 4-N-N-diethylamino-benzaldehyde in the presence of piperidine. The resultant material was kept in an oven, and the temperature was maintained around 100 °C

for 1 h. Afterwards, the DESI was purified by successive recrystallization from methanol. In a 250 ml beaker 2g of the DESI was dissolved in methanol. After getting the homogeneous solution it is sealed with appropriated cover and kept in the temperature bath. The growth temperature was maintained at 35 °C after a period of 10-15 days the crystals were harvested shown in Fig 1.

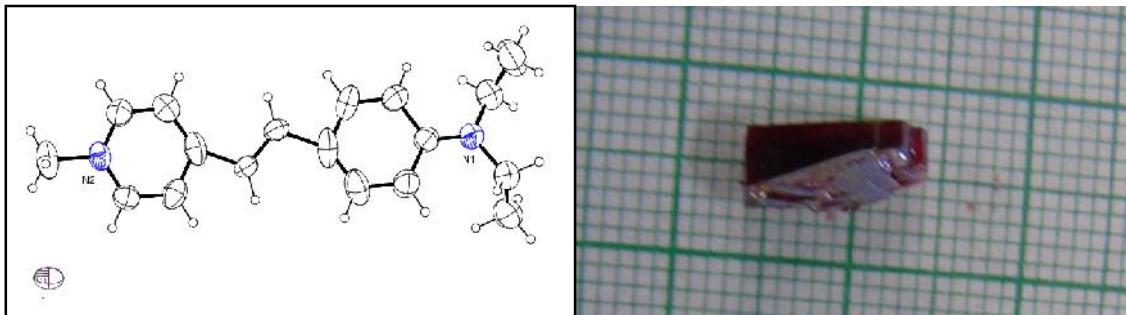


Figure 1- Ortep diagram and Photograph of DESI crystal

2. RESULTS AND DISCUSSION

2.1 Single crystal X-ray Diffraction analysis

The grown crystal was subjected to single crystal X-ray diffraction studies using Bruker Kappa APEXII single crystal X-ray diffractometer with MoK radiation ($\lambda = 0.7170 \text{ \AA}$) to solve the structure. The XRD data indicates that the crystal is triclinic structure and it belongs to centrosymmetric space group P-1. The calculated lattice parameters of grown DESI crystals are Unit cell dimensions $a = 7.8203(7) \text{ \AA}$, $b = 15.3176(15) \text{ \AA}$, $c = 17.1742(17) \text{ \AA}$, $\beta = 75.323(3)^\circ$, $\gamma = 87.401(3)^\circ$, $\delta = 89.396(3)^\circ$. Volume $1988.1(3) \text{ \AA}^3$

2.2 Optical absorption spectral analysis

The absorption spectra of the DESI crystal recorded in the solid phase as well as

in solution phase (methanol) are shown in Figure 2. It is observed that absorption spectrum of bulk crystalline DESI has a single strong absorbance band below 552 nm; which is due to J-type organization of chromophores within the crystalline structure of DESI. The absorption spectrum of DESI in methanol is different from that of crystalline form which shows two distinct absorption peaks. The minor peak at 271 nm corresponds to the $n \rightarrow \pi^*$ transition and the major peak with maximum absorption at around 487 nm represents the $\pi \rightarrow \pi^*$. The major absorption peak of the title compound in the visible region is good agreement with the stilbazolium chromophore with the unsaturated bond. Absence of absorption in the region between 487 and 800 nm for this crystal suggests it is an essential requirement for optoelectronics applications.

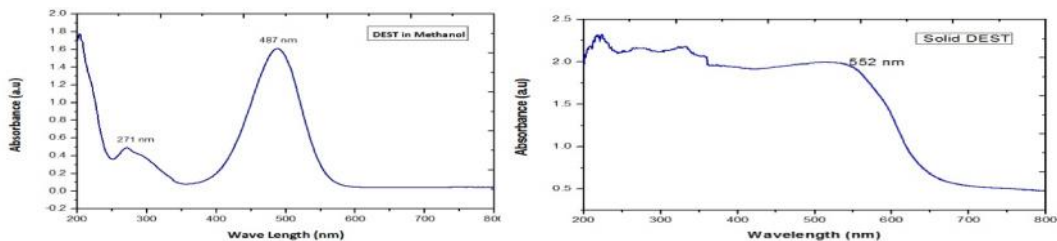


Figure 2- Absorption spectrum of DESI single crystal

Microhardness study

Mechanical strength of the materials plays a key role in device fabrication. During an indentation process, the external work applied by the indenter is converted to a strain energy component which is proportional to the volume of the resultant impression. The hardness of a material is influenced by various parameters such as the lattice energy, Debye temperature, heat formation and inter atomic spacing.

The Vickers hardness indentations were made on the as grown crystal of DESI. At room temperature, the load was varied as 10, 25, 50 and 100 grams for the slow evaporation grown

DESI crystal. The Vickers hardness number (H_v) was calculated using the relation,

$$H_v = 1.8544 (p/d^2) \text{ kg/mm}^2$$

Where, p is applied load and d is diagonal length of the indentations. The variations of H_v with the applied load p are shown in Figure 3a for grown crystal of DESI. The plot between $\log p$ vs $\log d$ for the crystals are shown in Figure 3b and it yields a straight line. The slope gives the work hardening index 'n', which is found to be 10 for grown sample. The microhardness study indicates that the crystal belongs to the class of soft materials. If $n < 2$, H_v decreases with increasing load (reverse indentation type), whereas for $n > 2$, H_v increases with load [5].

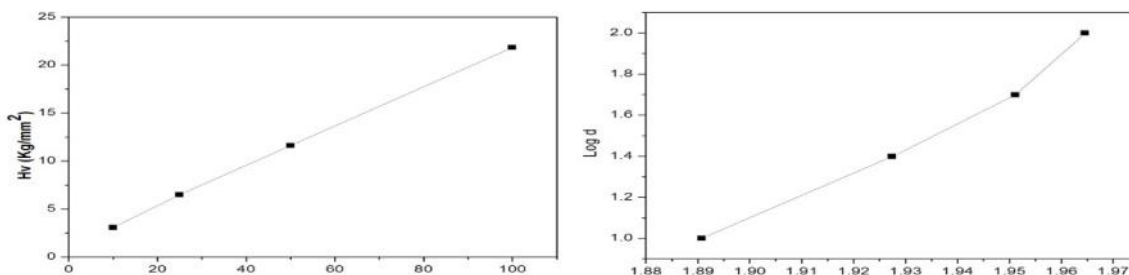


Figure 3a -Variation of H_v (Vickers hardness) with load (P) and 3b. Graph between $\log p$ vs $\log d$

ACKNOWLEDGEMENT

The authors acknowledge the DST-SERB, India for funding this research work (SR/S2/LOP-29/2013).

CONCLUSION

Organic stilbazolium family single DESI has been successfully grown from aqueous methanol solution by adopting slow solvent evaporation technique. Single crystal X-ray diffraction analysis was carried out and it shows that DESI crystal belongs to triclinic structure with P-1 space group. Its absorption spectrum was found by UV-Vis spectrum. Hardness study was also carried out for applying different loads and its found that the material belongs to soft material.

REFERENCES

[1]. Narissara Kaewmanee, Kullapa Chanawanno, Suchada Chantrapromma and

Hoong-Kun Fun, Acta Cryst. (2010). E66, o2639–o2640.

[2]. Jerald V. Ramaclus, Tina Thomas, S. Ramesh, P. Sagayaraj, E. A. Michael, CrystEngComm 16 (2014) 6889-6895.

[3]. K. Senthil, S. Kalainathan, A. Ruban Kumar, Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy 125 (2014) 335–344.

[4]. R. Jerald Vijay, N. Melikechi, Tina Thomas, R. Gunaseelan, M. Antony Arockiaraj, P. Sagayaraj, Mater. Chem. Phys. 132 (2012) 610-617.

[5]. K. Senthil, S. Kalainathan, A. Ruban Kumar, Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy 124 (2014) 603–610.